

Orbital Ordering and Resonant X-ray Scattering in Layered Manganites

Sumio Ishihara and Sadamichi Maekawa

Institute for Materials Research, Tohoku University, Sendai, 980-8577, Japan

(February 7, 2008)

In layered manganites with orbital and charge orderings, the degeneracy of the Mn 4*p* orbitals as well as the 3*d* ones is lifted by the effects of the 4*p* bands and the local Coulomb interactions. We formulate the atomic scattering factor for the resonant x-ray scattering in the memory function method by taking into account these effects on an equal footing. It is shown that the polarization dependences of the scattering intensities at the orbital and charge superlattice reflections observed in LaSr₂Mn₂O₇ are caused by the local and itinerant characters of 4*p* electrons, respectively. We examine the type of the orbital ordered state.

PACS numbers: 75.30.Vn, 71.10.-w, 78.70.Ck

Orbital degree of freedom is one of the key factors to uncover the dramatic and fruitful phenomena in colossal magnetoresistive (CMR) manganites. However, since the experimental technique to detect the orbital structure has been limited for a long time [1], it was considered to be a hidden degree of freedom. The resonant x-ray scattering (RXS) has recently shed light on this issue. Murakami *et al.* have applied the scattering method to La_{0.5}Sr_{1.5}MnO₄ and observed the superlattice reflections near the Mn³⁺ *K*-edge caused by the orbital ordering [2]. Immediately after the observation, this method was extensively studied in both the experimental and theoretical sides [3–8] and has been recognized to be a powerful tool to detect the orbital states through the application to several manganites.

Near the Mn³⁺ *K*-edge, RXS is given by the electric dipole transition between Mn 1*s* and 4*p* orbitals. The anomalous part of the atomic scattering factor (ASF) is a tensor with respect to the polarization of x-ray and the anisotropy of the tensor elements brings about the scattering at the orbital superlattice reflections. It was shown that the Coulomb interactions between Mn 3*d* and Mn 4*p* electrons and between Mn 3*d* and O 2*p* ones are the convincing candidates to induce the anisotropy in the orbital ordered states [7].

In this letter, we focus on RXS in manganites with layered structure. The layered manganites are recognized to be materials appropriate for studying orbital degree of freedom as well as CMR [9]. In double layered manganites La_{2–2*x*}Sr_{1+2*x*}Mn₂O₇, the orbital states are controlled by changing *x* and applying pressure and magnetic field [10–12]. The orbital states of 3*d* electrons as well as 4*p* ones depend on the deformation of the MnO₆ octahedron and the layered crystal structure. However, the octahedron is almost isotropic in the double layered manganites with *x* = 0.5 [13] where the orbital and charge orderings were recently observed by RXS [14]. Thus, the energy levels of the three 4*p* orbitals are nearly degenerate in the local sense. On the other hand, the layered structure provides the quasi-two dimensional character of the 4*p* band and lifts the degeneracy.

We formulate ASF in the memory function method by taking into account the effects of the 4*p* band and the local Coulomb interactions on an equal footing. The anisotropy of ASF reflected from the local and itinerant characters of the 4*p* electrons explains the experimental results in LaSr₂Mn₂O₇. Being based on the calculated results, types of the orbital ordered state are discussed.

Let us first formulate ASF. On resonance, the relevant term in the diagonal part of ASF is given by [15,7]

$$\Delta f_{\alpha} = \frac{m}{e^2} \sum_l \frac{\langle 0 | j_{i\alpha} | l \rangle \langle l | j_{i\alpha} | 0 \rangle}{\varepsilon_0 - \varepsilon_l + \omega - i\Gamma}, \quad (1)$$

where $|0\rangle$ ($|l\rangle$) denotes the initial (intermediate) electronic state with energy ε_0 (ε_l). ω is the energy of x-ray with polarization α . $j_{i\alpha} (= \frac{e}{m} A \sum_{\sigma} P_{i\alpha\sigma}^{\dagger} s_{i\sigma} + H.c.)$ describes the 1*s* → 4*p* transition where $P_{i\alpha\sigma}^{\dagger}$ and $s_{i\sigma}$ are the creation operator of Mn 4*p* electron at site *i* with spin σ and orbital $\alpha (= x, y, z)$ and the annihilation one of Mn 1*s* electron, respectively. Γ denotes the damping of a core hole. Because the radius of the Mn 1*s* orbital is much smaller than the lattice constant, the 1*s* electron is excited to the 4*p* orbital at the same site. The relevant part of Δf_{α} is rewritten by using the Green's function for the operator $J_{i\alpha\sigma} = P_{i\alpha\sigma}^{\dagger} s_{i\sigma}$ as follows,

$$\text{Im} \Delta f_{\alpha} = -\frac{e^2 |A|^2}{m} \sum_{\sigma} \text{Im} G_{\alpha\sigma}(z) \Big|_{z=\omega+i\Gamma}, \quad (2)$$

where $G_{\alpha\sigma}(z)$ is the Fourier transform (FT) of the retarded Green's function $G_{\alpha\sigma}(t) = \frac{i}{2\pi} \int e^{-i\omega t} G_{\alpha\sigma}(\omega) d\omega$ defined by $G_{\alpha\sigma}(t) = \theta(t) \langle [J_{i\alpha\sigma}^{\dagger}(t), J_{i\alpha\sigma}(0)] \rangle$.

We consider a MnO₆ cluster where x-ray is absorbed. The electrons in the cluster couple to the 4*p* bands. The Hamiltonian is given by $H = H_0 + H_{4p}$, with

$$\begin{aligned} H_0 = & \varepsilon_d \sum_{\gamma\sigma} d_{i\gamma\sigma}^{\dagger} d_{i\gamma\sigma} + \varepsilon_p \sum_{\gamma\sigma} p_{i\gamma\sigma}^{\dagger} p_{i\gamma\sigma} + \varepsilon_s \sum_{\sigma} s_{i\sigma}^{\dagger} s_{i\sigma} \\ & + t_{pd} \sum_{\gamma\sigma} (d_{i\gamma\sigma}^{\dagger} p_{i\gamma\sigma} + p_{i\gamma\sigma}^{\dagger} d_{i\gamma\sigma}) \\ & + U \sum_{\gamma} n_{i\gamma\uparrow}^d n_{i\gamma\downarrow}^d + U' \sum_{\sigma\sigma'} n_{ia\sigma}^d n_{ib\sigma'}^d \end{aligned}$$

$$\begin{aligned}
& + I \sum_{\sigma\sigma'} d_{i\alpha\sigma}^\dagger d_{ib\sigma'}^\dagger d_{ia\sigma'} d_{ib\sigma} - J_H \vec{S}_i \cdot \vec{S}_{ti} \\
& + n_h \sum_{\gamma\sigma} (V_{sd} n_{i\gamma\sigma}^d + V_{sp} n_{i\alpha\sigma}^P) + \sum_{\alpha\gamma\sigma\sigma'} V_{\gamma\alpha} n_{i\gamma\sigma}^d n_{i\alpha\sigma'}^P, \quad (3)
\end{aligned}$$

and

$$H_{4p} = \varepsilon_P \sum_{j\alpha\sigma} P_{j\alpha\sigma}^\dagger P_{j\alpha\sigma} + \sum_{j\delta\alpha\beta\sigma} t_\alpha^\beta P_{j\alpha\sigma}^\dagger P_{j+\delta\beta\alpha\sigma}, \quad (4)$$

where H_0 and H_{4p} describe the electronic states in the MnO_6 cluster and in the $4p$ band, respectively [16]. i indicates the site where x-ray is absorbed. $d_{i\gamma\sigma}$ is the annihilation operator of Mn $3d$ electron with spin σ and orbital $\gamma (= 3z^2 - r^2, x^2 - y^2)$ and $p_{i\gamma\sigma}$ is that of O $2p$ electron with σ and γ represented by combining six O $2p$ orbitals in a MnO_6 octahedron [7]. The number operator of Mn $3d$ ($4p$) electrons and that of core holes are denoted by $n_{i\gamma\sigma}^d$ ($n_{i\alpha\sigma}^P$) and n_{ih} , respectively. The last three terms in Eq. (3) describe the the core hole potentials and the Coulomb interaction between $3d$ and $4p$ electrons, respectively. The explicit form of $V_{\gamma\alpha}$ is given by $V_{\gamma\alpha} = F_0 + 4F_2 \cos(\theta_\gamma + m_\alpha \frac{2\pi}{3})$ with the angle in the orbital space θ_γ defined by $|\theta_\gamma\rangle = \cos(\theta_\gamma/2)|d_{3z^2-r^2}\rangle + \sin(\theta_\gamma/2)|d_{x^2-y^2}\rangle$ and $(m_x, m_y, m_z) = (1, 2, 3)$ [7]. This interaction directly connects the orbital states of $3d$ electrons with that of $4p$ ones. The crystal with layered structure is described by the tetragonal lattice in H_{4p} . t_α^β is the hopping integral between the site j with orbital α and its nearest neighboring site $j + \delta_\beta$ with α , where δ_β indicates a bond in the β direction. The following conditions are satisfied: $t_x^x = t_y^y \equiv t_\sigma^\parallel$, $t_x^z = t_y^z = t_y^x = t_x^y \equiv t_\pi^\parallel$, $t_z^z \equiv t_\sigma^\perp$ and $t_x^z = t_y^z \equiv t_\pi^\perp$. The effect of the lattice distortion [8] is neglected, since it is experimentally confirmed to be small in the layered manganites around $x = 0.5$ [13]. Thus, $\varepsilon_{d(p)}$ and ε_P are chosen to be independent of γ and α , respectively. The inter-site Coulomb interaction between Mn $4p$ and O $2p$ electrons is not included, because the interaction brings about the anisotropy of ASF in the similar way as $V_{\gamma\alpha}$ [7].

The memory function method (the composite operator method) in the Green's function formalism is adopted in the calculation of ASF. This method is suitable to describe the excitation in the highly correlated systems [17,18] and treats the local Coulomb interactions and the $4p$ band on an equal footing. We introduce the relaxation function defined by $C_{\alpha\sigma}(t) = \theta(t)\beta^{-1} \int_0^\beta d\lambda \langle J_{i\alpha\sigma}^\dagger(t) J_{i\alpha\sigma}(i\lambda) \rangle \equiv \theta(t) \langle J_{i\alpha\sigma}^\dagger(t) J_{i\alpha\sigma}(0) \rangle_\lambda$ with $\beta = 1/T$. We have $\text{Im}C_{\alpha\sigma}(\omega) = \text{Im}G_{\alpha\sigma}(\omega)/(\beta\omega)$, $C_{\alpha\sigma}(\omega)$ being FT of $C_{\alpha\sigma}(t)$. At the end of the calculation, we take $T = 0$. The final form of $C_{\alpha\sigma}(\omega) (\equiv \delta M_C^{(0)}(\omega))$ is given by the continued fraction [18]:

$$\delta M_C^{(n-1)}(\omega) = \frac{I^{(n)}}{\omega - (M_0^{(n)} + \delta M^{(n)}(\omega))I^{(n-1)}}, \quad (5)$$

with $\delta M^{(n)}(\omega) = \delta M_B^{(n)}(\omega) + \delta M_C^{(n)}(\omega)$ for $n > 1$. $\delta M_C^{(n-1)}(\omega)$ is given by FT of $\delta M_C^{(n-1)}(t) = \theta(t) \langle \psi_n^\dagger(t) \psi_n(0) \rangle_\lambda$. $\delta M^{(3)}(\omega)$ is taken to be zero and the continued fraction is truncated at $n = 3$. Here, ψ_n is the composite operator represented by an operator product [19]. $\psi_1 = J_{i\alpha\sigma}$ and ψ_{n+1} appears in the equation of motion of ψ_n . $I^{(n)} (= \langle \psi_n^\dagger \psi_n \rangle_\lambda)$ and $M_0^{(n)} (= \langle (i\partial_t \psi_n^\dagger) \psi_n \rangle_\lambda)$ correspond to the normalization factor and the static part of the self-energy, respectively. $\delta M_B^{(n)}(\omega)$ is the relaxation function including operators at site $j \neq i$, such as $P_{j\alpha\sigma}^\dagger s_{i\sigma}$. The detailed formulation will be presented elsewhere. Advantages of this method in the present issue are the following: 1) The many body excitations originating from the local Coulomb interactions are treated by the composite operators. For example, $P_{i\alpha\sigma}^\dagger s_{i\sigma} d_{i\gamma\sigma'}^\dagger p_{i\gamma\sigma'}$ describes the dipole transition associated with the charge transfer between Mn $3d$ and O $2p$ orbitals. By treating ψ_n as a single quantum variable, the many body excitations and the interactions between them, i.e. so-called the configuration interactions, are taken into account in $\delta M_C^{(n)}(\omega)$ and $M_0^{(n)}$. This kind of the excitation is not treated by the independent single-particle scheme with an averaged potential. 2) The band effects of the $4p$ electrons are included in $\delta M_B^{(n)}(\omega)$. By adopting the loop approximation in the diagram technique, where the $4p$ state is treated as the single-particle state described by H_{4p} , the itinerant character of the excitation is introduced. This kind of excitation plays a crucial role on ASF in the present case where the layered structure lifts the orbital degeneracy and is not described by the calculation in a small cluster.

The calculated ASF is presented in Fig. 1(a), where the $d_{3x^2-y^2}$ orbital is occupied. The $[d_{3x^2-r^2}/d_{3y^2-r^2}]$ -type orbital ordered states, where the two orbitals are alternately aligned in the xy plane, is assumed. The anisotropy of the $4p$ band is characterized by $t_\sigma^\parallel/t_\sigma^\perp = 4$ and $t_\pi^\parallel/t_\pi^\perp = t_\sigma^\perp/t_\pi^\perp = 4$ [20]. A continuous spectrum in $\text{Im}\Delta f_{x(y)}$ spreads over a wide region of ω . The weight near the K -edge is dominated by $\text{Im}\Delta f_{x(y)}$, because the $4p_{x(y)}$ band is wider than the $4p_z$ band; the quasi-two dimensional band of the $4p$ electrons causes the anisotropy between $\Delta f_{x(y)}$ and Δf_z . However, it is worth to note that $\text{Im}\Delta f_\alpha$ is not the density of states itself. There are several peak structures in $\text{Im}\Delta f_\alpha$ caused by the local excitations in the MnO_6 cluster. Near the edge, the clear anisotropy between $\text{Im}\Delta f_x$ and $\text{Im}\Delta f_y$ appears and $\text{Im}\Delta f_y$ governs the intensity. This anisotropy is caused by the Coulomb interaction between $3d$ and $4p$ electrons. The core hole potential makes the anisotropy remarkable, since the potential reduces the energy of the dipole transition and enhances the local character of the $4p$ electrons. The scattering intensity at the orbital superlattice reflection defined by $I_O(\phi = \pi/2) = |\Delta f_x - \Delta f_y|^2 / (2|A|^2 / mt_{pd})^2$ [7,21] is shown in the inset

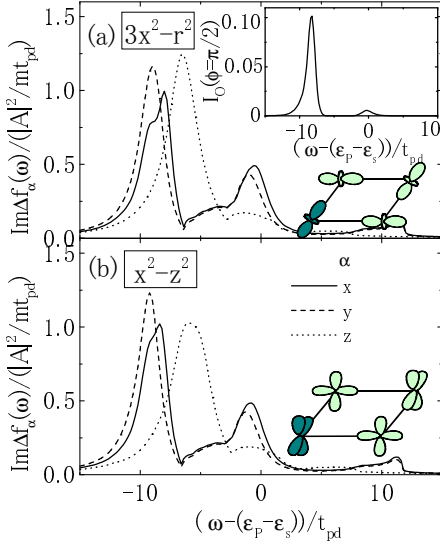


FIG. 1. The imaginary part of ASF. (a) The $d_{3x^2-r^2}$ orbital is occupied in the $[d_{3x^2-r^2}/d_{3y^2-r^2}]$ -type orbital ordered state. The straight, dashed and dotted lines show ASF for $\alpha = x, y$ and z , respectively. (b) The $d_{x^2-z^2}$ orbital is occupied in the $[d_{x^2-z^2}/d_{y^2-z^2}]$ -type orbital ordered state. The insets show the scattering intensity at the orbital superlattice reflection and schematic pictures of the orbital ordered states.

of Fig. 1(a). Here, the azimuthal angle (ϕ) is the rotating one of the sample around the scattering vector. For $\phi = 0$ ($\pi/2$), the electric vector of x-ray is perpendicular (parallel) to the xy plane. A sharp peak near the edge together with a small intensity above the edge appear in $I_O(\phi)$. Both structures are observed in $\text{LaSr}_2\text{Mn}_2\text{O}_7$ [14]. In Fig. 1(b), we show ASF at the site where the $d_{x^2-z^2}$ orbital is occupied in the $[d_{x^2-z^2}/d_{y^2-z^2}]$ -type orbital ordered state. The anisotropy between $\text{Im}\Delta f_{x(y)}$ and $\text{Im}\Delta f_z$ becomes more remarkable near the edge due to the Coulomb interaction.

The anisotropies of ASF directly reflect on the polarization dependence of the scattering intensity. Let us consider the charge and orbital ordered states realized in the layered manganite at $x = 0.5$ [2,14]. The scattering intensities at the orbital and charge reflection points in the $[\theta/-\theta]$ -type orbital ordered state are given by $I_O(\phi) = |(\Delta f_x - \Delta f_y) \sin \phi|^2 / (2|A|^2/mt_{pd})^2$ and $I_C(\phi) = |(\Delta f_x + \Delta f_y) \sin^2 \phi + 2\Delta f_z \cos^2 \phi|^2 / (2|A|^2/mt_{pd})^2$, respectively [7,21]. The polarization dependences of $I_O(\phi)$ and $I_C(\phi)$ are attributed to the anisotropies between Δf_x and Δf_y due to the local Coulomb interactions and between $\Delta f_x + \Delta f_y$ and Δf_z due to the effects of the $4p$ band, respectively; the itinerant and local characters of the excited $4p$ electrons reflect on $I_C(\phi)$ and $I_O(\phi)$, respectively. The theoretical results of $I_O(\phi)$ and $I_C(\phi)$ near the edge are plotted together with the experimental data in $\text{LaSr}_2\text{Mn}_2\text{O}_7$ [14] in Fig. 2. We find good

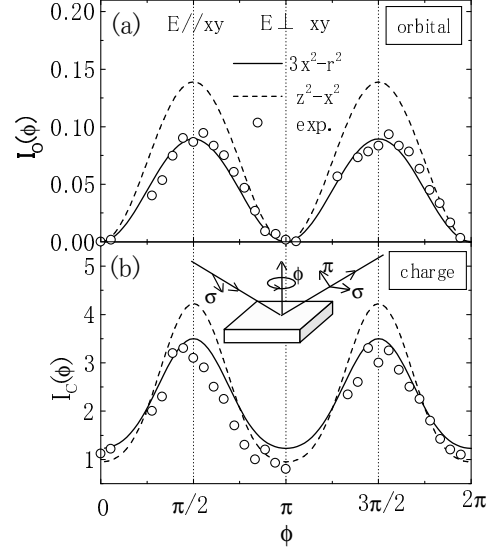


FIG. 2. The polarization dependence of the scattering intensities at the orbital superlattice reflection (a) and at the charge superlattice one (b) near the edge ($(\omega - (\epsilon_P - \epsilon_s))/t_{pd} = -9.6$). The straight and broken lines show the intensities in the $[d_{3x^2-r^2}/d_{3y^2-r^2}]$ - and $[d_{x^2-z^2}/d_{y^2-z^2}]$ -type orbital ordered states, respectively. The open circles show the experimental data obtained in $\text{LaSr}_2\text{Mn}_2\text{O}_7$ [14]. Absolute values of the experimental data are arbitrary. The inset shows the schematic picture of the experimental arrangement.

agreement with theory and experiment. Thus, we conclude that ASF in $\text{LaSr}_2\text{Mn}_2\text{O}_7$ near the edge is dominated by $\Delta f_{x(y)}$ and the degeneracy between Δf_x and Δf_y is lifted by the Coulomb interactions in the $[\theta/-\theta]$ -type orbital ordered state. On the other hand, the θ -dependence of ASF is not so remarkable as to determine the value of θ . However, from the following facts, we deduce that the $[d_{3x^2-r^2}/d_{3y^2-r^2}]$ -type ($\theta = 2\pi/3$) ordered state is more favorable in $\text{LaSr}_2\text{Mn}_2\text{O}_7$ rather than the $[d_{x^2-z^2}/d_{y^2-z^2}]$ -type one; In the layered structure, the $[d_{3x^2-r^2}/d_{3y^2-r^2}]$ -type ordered state gains more kinetic energy than the $[d_{x^2-z^2}/d_{y^2-z^2}]$ -type one, because the $3d$ band in the former state is wider than that in the latter, as discussed in the case of the $4p$ band. This is consistent with the zigzag-type ferromagnetic spin alignment observed in the xy plane [13]. In the $[d_{3x^2-r^2}/d_{3y^2-r^2}]$ -type ordered state, the hopping integral in the z direction is small, where the same kinds of charge and orbital are stacked [14]. As a result, the double exchange interaction in this direction is suppressed and the superexchange interaction between t_{2g} spins causes the antiferromagnetic spin alignment as observed experimentally [13].

The anisotropy of ASF in the layered structure is quite different from that in the cubic structure where the $4p$ band does not contribute to the anisotropy. ASF calculated on the condition $t_{\sigma}^{\parallel}/t_{\sigma}^{\perp} = t_{\pi}^{\parallel}/t_{\pi}^{\perp} = 1$ is shown in

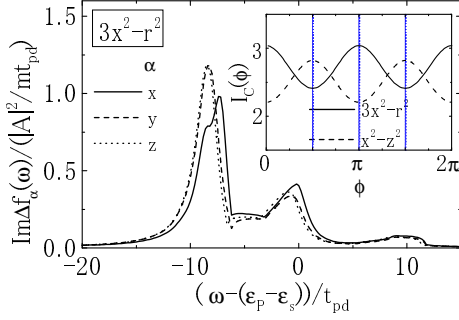


FIG. 3. The imaginary part of ASF. The isotropic $4p$ band is assumed. The $d_{3x^2-r^2}$ orbital is occupied in the $[d_{3x^2-r^2}/d_{3y^2-r^2}]$ -type orbital ordered states. The straight, dashed and dotted lines show ASF for $\alpha = x, y$ and z , respectively. $\text{Im}\Delta f_y$ and $\text{Im}\Delta f_z$ are almost degenerate. The inset shows the polarization dependence of the scattering intensity at the charge superlattice reflection $I_C(\phi)$. The straight and broken lines show $I_C(\phi)$ for the $[d_{3x^2-r^2}/d_{3y^2-r^2}]$ - and $[d_{x^2-z^2}/d_{y^2-z^2}]$ -type orbital ordered states, respectively.

Fig. 3 where the $d_{3x^2-r^2}$ orbital is occupied. Δf_y and Δf_z are almost degenerate and the anisotropy between $\Delta f_{y(z)}$ and Δf_x is provided by the local Coulomb interaction, as shown in the previous results obtained in the MnO_6 cluster [7]. The energy and polarization dependences of I_O are similar to those in the inset of Fig. 1(a) and Fig. 2(a), respectively. $I_C(\phi)$ depends on types of the orbital ordered state (the inset of Fig. 3) [22,7].

The anisotropy of ASF in the layered manganites is highly in contrast to that in the layered nickelates and cuprates. In the latter compounds, the K -edge is dominated by the z component and the $x(y)$ component is located above $2 \sim 10$ eV from the edge [23,24]. Since the octahedron is elongated along the z axis (more than 20% in cuprates and 15% in nickelates), the large hybridization between $4p_{x(y)}$ and $\text{O}2p$ orbitals pushes the $4p_{x(y)}$ band to the higher energy region. On the contrary, in the layered manganites around $x = 0.5$, the elongation is less than 1% [13] and the orbital degree of freedom for the $4p$ electrons survives in the local sense as well as that for the $3d$ ones. Thus, contribution from the quasi-two dimensional band is relevant near the edge.

To conclude, we have studied RXS in layered manganites by taking into account the effects of the $4p$ bands and the local Coulomb interactions. The anisotropies between $\Delta f_{x(y)}$ and Δf_z and between Δf_x and Δf_y are reflected from the local and itinerant characters of the $4p$ electrons, respectively. The calculated results well reproduce the experimental ones in $\text{LaSr}_2\text{Mn}_2\text{O}_7$.

Authors thank Y. Murakami and Y. Wakabayashi for providing the experimental data prior to publication, T. Arima and Y. Endoh for their valuable discussions. The work was supported by CREST and NEDO. Part of the numerical calculation was performed in the HITACS-3800/380 supercomputing facilities in IMR, Tohoku Univ.

- [1] Y. Ito, and J. Akimitsu, J. Phys. Soc. Jpn. **40**, 1333 (1976).
- [2] Y. Murakami *et al.*, Phys. Rev. Lett. **80**, 1932 (1998).
- [3] Y. Murakami *et al.*, Phys. Rev. Lett. **81**, 582 (1998).
- [4] Y. Endoh *et al.*, Phys. Rev. Lett. **82**, 4328 (1999).
- [5] K. Nakamura *et al.*, Phys. Rev. B **60**, (1999).
- [6] M. v. Zimmermann *et al.*, cond-mat/9905285.
- [7] S. Ishihara, and S. Maekawa, Phys. Rev. Lett. **80**, 3799 (1998), and Phys. Rev. B **58**, 13449 (1998).
- [8] I. S. Elfimov *et al.*, Phys. Rev. Lett. **82**, 4264 (1999), M. Benfatto *et al.* Phys. Rev. Lett. (to be published), M. Takahashi *et al.*, (unpublished).
- [9] H. Moritomo *et al.*, Nature (London) **380**, 141 (1996).
- [10] T. Kimura *et al.*, Phys. Rev. Lett. **79**, 3720 (1997), *ibid.* **81**, 5920 (1998).
- [11] D. N. Argyriou *et al.*, Phys. Rev. B **55**, R11965 (1997).
- [12] S. Ishihara *et al.*, J. Phys. Soc. Jpn. **66** 2965 (1997).
- [13] M. Kubota *et al.*, cond-mat/9902288, and J. Phys. Soc. Jpn. **68** 2202 (1999).
- [14] Y. Wakabayashi *et al.*, (unpublished).
- [15] M. Blume, J. Appl. Phys. **57**, 3615 (1985).
- [16] $\tilde{S}_i$ ($\tilde{S}_{ti}$) is the spin operator for the e_g (t_{2g}) electrons. U (U'), I and J_H are the intra (inter)-orbital Coulomb interaction, the exchange interaction and the Hund coupling between e_g and t_{2g} spins, respectively.
- [17] D. Forster, in *Hydrodynamic Fluctuations, Broken Symmetry and Correlation Functions* (Addison-Wesley, Massachusetts, 1990), and P. Fulde, in *Electron Correlations in Molecules and Solids* (Springer-Verlag, Berlin, 1993).
- [18] H. Matsumoto *et al.*, Phys. Rev. B **46** 3009, (1992), and S. Ishihara *et al.*, Phys. Rev. B **49**, 1350 (1994).
- [19] The three operators: $(\psi_1, \psi_2, \psi_3) = (J_{i\alpha\sigma}, P_{i\alpha\sigma}^\dagger s_{i\sigma} \delta n_{i\gamma}^d, P_{i\alpha\sigma}^\dagger s_{i\sigma} \delta n_{i\gamma}^{dp})$ are adopted as the composite operators, where $\delta A = A - \langle A \rangle$ and $n_{i\gamma}^{dp} = \sum_{\sigma} d_{i\gamma\sigma}^\dagger p_{i\gamma\sigma}$. $\delta M_B^{(n)}(\omega)$ is the relaxation function of the operators: $(P_{j\alpha\sigma}^\dagger s_{i\sigma}, P_{j\alpha\sigma}^\dagger s_{i\sigma} \delta n_{i\gamma}^d, P_{j\alpha\sigma}^\dagger s_{i\sigma} \delta n_{i\gamma}^{dp})$ for $n = (1, 2, 3)$ where j indicates the nearest neighboring site of i .
- [20] The other parameter values are chosen to be $\varepsilon_p - \varepsilon_d = 1.5$, $U = 5$, $U' = 4$, $J_H = I = 1$, $V_{sd} = -5.0$, $V_{sp} = -3.5$, $F_0 = 3.5$, $F_2 = 0.25$, $t_{\sigma}^{\parallel} = 3$ and $\Gamma = 1.5$ in units of t_{pd} with t_{pd} being about 1eV.
- [21] The polarization of the scattered x-ray is chosen to be the π (σ) component for $I_O(\phi)$ ($I_C(\phi)$). Contribution from the Mn^{4+} ion to $I_C(\phi)$ is neglected, since it is small near the Mn^{3+} K -edge.
- [22] We note that manganites with cubic structure and the charge ordering at $x \sim 0.5$ have a two dimensional character which provides the anisotropy between $\Delta f_{x(y)}$ and Δf_z , as shown in the layered case.
- [23] A. Sahiner *et al.*, Phys. Rev. B **51**, 5879 (1995).
- [24] J. P. Hill *et al.*, Phys. Rev. Lett. **80**, 4967 (1998).